

# DIGITALES ARCHIV

ZBW – Leibniz-Informationszentrum Wirtschaft  
ZBW – Leibniz Information Centre for Economics

Lokatkina, Anastasiia; Prikhna, Tetiana; Moshchil, Viktor et al.

## Article

### Influence of heating to high temperatures on mechanical properties of boride-based refractory materials

*Reference:* Lokatkina, Anastasiia/Prikhna, Tetiana et. al. (2021). Influence of heating to high temperatures on mechanical properties of boride-based refractory materials. In: Technology audit and production reserves 2 (1/58), S. 21 - 25.

<http://journals.uran.ua/tarp/article/download/228943/229201/525656>.

doi:10.15587/2706-5448.2021.228943.

This Version is available at:

<http://hdl.handle.net/11159/6853>

## Kontakt/Contact

ZBW – Leibniz-Informationszentrum Wirtschaft/Leibniz Information Centre for Economics

Düsternbrooker Weg 120

24105 Kiel (Germany)

E-Mail: [rights\[at\]zbw.eu](mailto:rights[at]zbw.eu)

<https://www.zbw.eu/econis-archiv/>

## Standard-Nutzungsbedingungen:

Dieses Dokument darf zu eigenen wissenschaftlichen Zwecken und zum Privatgebrauch gespeichert und kopiert werden. Sie dürfen dieses Dokument nicht für öffentliche oder kommerzielle Zwecke vervielfältigen, öffentlich ausstellen, aufführen, vertreiben oder anderweitig nutzen. Sofern für das Dokument eine Open-Content-Lizenz verwendet wurde, so gelten abweichend von diesen Nutzungsbedingungen die in der Lizenz gewährten Nutzungsrechte.

<https://zbw.eu/econis-archiv/termsfuse>

## Terms of use:

*This document may be saved and copied for your personal and scholarly purposes. You are not to copy it for public or commercial purposes, to exhibit the document in public, to perform, distribute or otherwise use the document in public. If the document is made available under a Creative Commons Licence you may exercise further usage rights as specified in the licence.*

**Anastasiia Lokatkina,  
Tetiana Prikhna,  
Viktor Moshchil,  
Pavlo Barvitskyi,  
Oleksandr Borimsky,  
Leonid Devin,  
Semyon Ponomaryov,  
Richard Haber,  
Tatiana Talako,  
Anatoly Bondar**

## INFLUENCE OF HEATING TO HIGH TEMPERATURES ON MECHANICAL PROPERTIES OF BORIDE-BASED REFRACTORY MATERIALS

The object of research is  $HfB_2$ ,  $ZrB_2$  and ceramics composition  $HfB_2$ -30 % SiC and  $ZrB_2$ -20 % SiC,  $ZrB_2$ -20 % SiC-4 %  $Si_3N_4$  obtained under high pressure, their mechanical characteristics before and after heating to high temperatures and temperatures of beginning of melting. The research was conducted in order to create new effective refractory materials for use in the aerospace industry. Therefore, the melting temperatures of sintered materials and the effect of heating on their mechanical properties were also studied. Additives ( $ZrB_2$ -20 % SiC and  $HfB_2$ -30 % SiC) although led to a decrease in specific gravity. But increased hardness (by 17 % and 46 % in the case of  $ZrB_2$  and  $HfB_2$ , respectively) and fracture toughness (by 40 % and 21 % in the case of  $ZrB_2$  and  $HfB_2$ , respectively). However, significantly reduced the onset of melting temperature in vacuum to 2150–2160 °C.

Materials sintered from  $ZrB_2$  and  $HfB_2$  was not melted after heating to 2970 °C. After heating to a melting point of 2150–2160 °C (in the case of materials with additives) and to temperatures of 2970 °C (in the case of materials sintered with  $ZrB_2$  or  $HfB_2$ ), the hardness and fracture toughness decreased. Thus, the hardness of the material prepared from  $ZrB_2$  decreased by 19 % and its fracture toughness – by 18 %, and of that prepared from  $ZrB_2$ -20 % SiC – by 46 % and 32 %, respectively. The hardness of the material prepared from  $HfB_2$  decreased by 46 %, its fracture toughness – by 55 %, and of that prepared from  $HfB_2$ -30 % SiC, after heating decreased by 40 %, but its fracture toughness increased by 15 %. The sintered  $HfB_2$  (with a density of 10.4 g/cm<sup>3</sup>) before heating showed a hardness of  $H_V(9.8 N)=21.27\pm 0.84$  GPa,  $H_V(49 N)=19.29\pm 1.34$  and  $H_V(98 N)=19.17\pm 0.5$ , and fracture toughness  $K_{1C}(9.8 N)=0.47$  MH·m<sup>0.5</sup>, and  $ZrB_2$  with a density of 6.2 g/cm<sup>3</sup> was characterized by  $H_V(9.8 N)=17.66\pm 0.60$  GPa,  $H_V(49 N)=15.25\pm 1.22$  GPa and  $H_V(98 N)=15.32\pm 0.36$  GPa,  $K_{1C}(9.8 N)=4.3$  MH·m<sup>0.5</sup>. Material sintered with  $HfB_2$ -30 % SiC (density 6.21 g/cm<sup>3</sup>) had  $H_V(9.8 N)=38.1\pm 1.4$  GPa,  $H_V(49 N)=27.7\pm 2.8$  GPa, and  $K_{1C}(9.8 N)=8.1$  MH·m<sup>0.5</sup>,  $K_{1C}(49 H)=6.8$  MH·m<sup>0.5</sup>. The sintered with  $ZrB_2$ -20 % SiC material had density of 5.04 g/cm<sup>3</sup>,  $H_V(9.8 N)=24.2\pm 1.9$  GPa,  $H_V(49 N)=16.7\pm 2.8$  GPa,  $K_{1C}(49 H)=7.1$  MH·m<sup>0.5</sup>. The SiC addition to the initial mixture significantly reduces the elasticity of the materials.

**Keywords:** zirconium diboride, hafnium diboride, silicon carbide, silicon nitride, ultrahigh-temperature ceramics, refractory borides.

Received date: 11.01.2021

Accepted date: 23.02.2021

Published date: 30.04.2021

© The Author(s) 2021

This is an open access article

under the Creative Commons CC BY license

### How to cite

Lokatkina, A., Prikhna, T., Moshchil, V., Barvitskyi, P., Borimsky, O., Devin, L., Ponomaryov, S., Haber, R., Talako, T., Bondar, A. (2021). Influence of heating to high temperatures on mechanical properties of boride-based refractory materials. *Technology Audit and Production Reserves*, 2 (1 (58)), 21–25. doi: <http://doi.org/10.15587/2706-5448.2021.228943>

### 1. Introduction

The IV–V groups of diborides and carbides of transition metals have a very high melting point (>2500 °C), high mechanical properties, hardness, fracture toughness and high thermal properties, and therefore are recommended as ultra-high temperature ceramics (UHTC) [1–3]. As a result, this material has been proposed for a variety of structural

applications at room and elevated temperature including aerospace applications.

SiC reinforcement of  $ZrB_2$  is known [4] to increase flexural strength, fracture toughness and oxidation resistance and so was chosen as additive in this study. Hafnium diboride has several important advantages over  $ZrB_2$ . The fundamental difference in nuclear properties is thermal the neutron capture cross section in hafnium compounds is 3 orders

of magnitude higher than that of zirconium compounds. The relatively high density of HfB<sub>2</sub> (11.20 vs. 6.12 g/cm<sup>3</sup> in ZrB<sub>2</sub>), according to the authors [5], is not a disadvantage and, conversely, can be useful for moving the center of gravity of the High-Lift System Aerodynamics forward in some aerodynamic schemes.

The object of research is HfB<sub>2</sub>, ZrB<sub>2</sub> and ceramics composition HfB<sub>2</sub>-30 % SiC and ZrB<sub>2</sub>-20 % SiC, ZrB<sub>2</sub>-20 % SiC-4 % Si<sub>3</sub>N<sub>4</sub> obtained under high pressure, their mechanical characteristics before and after heating to high temperatures and temperatures of beginning of melting. The aim of research is study the melting temperatures of sintered materials and the effect of heating on their mechanical properties.

## 2. Methods of research

Under high 4.1 GPa pressure at 1800 °C temperature were prepared samples of ZrB<sub>2</sub>, HfB<sub>2</sub>, ZrB<sub>2</sub>-20 % SiC, ZrB<sub>2</sub>-20 % SiC-4 % Si<sub>3</sub>N<sub>4</sub>, HfB<sub>2</sub>-30 % SiC which were approximately 15 mm in diameter and 7 mm in height. During sintering, there were 10 samples. The sintered material was in contact with graphite and hexagonal boron nitride.

Table 1 shows the results of X-ray study of phase composition of initial ZrB<sub>2</sub> (Technical specification 6-09-03-46-75), HfB<sub>2</sub> (Ukraine, Technical specification 6-09-03-418-75) powders (with grain sizes <10 μm which contained 0.1 mass % and 0.2 mass % of admixture carbon, respectively). Additions of SiC and Si<sub>3</sub>N<sub>4</sub> were mixed with diborides using a «drunken barrel» mixer for 24 hours.

The samples structure was studied by X-ray diffraction using a DRON-UM1 diffractometer (USSR). To define the phase composition, the monochromatic CuKα radiation (λ=1.541841 Å) in the range of angles 2Θ=8°–88° with a scan step of 0.05° and a time of the exposition at a point of 2 s. As a monochromatic a graphite single crystal installed on a diffracted beam was used. The analysis of the experimental data was made using the PowderCell 2.4 programs, in which the full profile refinement by the Rietveld method was realized [6].

Table 1  
Unit cell parameters *a*, *b*, *c* and phase composition of the initial powders

Initial powder	Phase composition, mass. %	<i>a</i> , <i>b</i> , <i>c</i> , nm
ZrB <sub>2</sub>	ZrB <sub>2</sub> – 97 %	<i>a</i> – 0.3168, <i>c</i> – 0.3530
	ZrO <sub>2</sub> t – 1 %	<i>a</i> – 0.3604, <i>c</i> – 0.5208
	ZrO <sub>2</sub> m – 2 %	<i>a</i> – 0.5153, <i>b</i> – 0.5210, <i>c</i> – 0.5310
HfB <sub>2</sub>	HfB <sub>2</sub> – 100 %	<i>a</i> – 0.3143, <i>c</i> – 0.3476
Si <sub>3</sub> N <sub>4</sub>	A – Si <sub>3</sub> N <sub>4</sub> – 4 %	<i>a</i> – 0.7747, <i>c</i> – 0.5620
	B – Si <sub>3</sub> N <sub>4</sub> – 96 %	<i>a</i> – 0.7599, <i>c</i> – 0.2907
SiC	3C – SiC – 100 %	–

Vickers microhardness and fracture toughness were determined using a FALCON 500 hardness tester (Netherlands) (equipped with an optical microscope, a digital 5-megapixel camera, and a computer). At least 5 indents were made at a load of 9.8 N, 49 N, 98 N.

The modulus of elasticity was calculated according to the method described in [7, 8], using a solution for the lower mode of oscillations of the disks, as it has the greatest practical interest due to the high reliability of the method of recording resonance.

The temperatures of incipient melting were determined with the Pirani-Alterthum technique [9] employing an EOP-68 pyrometer (made by Kharkiv Experimental Plant «Pribor», Ukraine). The instrumental errors of the device are ±4 °C in the range 1400–2000 °C and ±12 °C at 2000–3000 °C.

The Pirani-Alterthum technique and evaluation of measurement errors are described in detail elsewhere [10, 11].

## 3. Research results and discussion

Table 2 shows the compositions of the initial mixtures, parameters of sintering, the phase composition of the consolidated materials, and the unit cell parameters of the present in the materials phases, determined by X-ray diffraction analysis. Table 3 shows the results of tests of hardness and fracture toughness of materials before and after heating to the temperatures of beginning of melting or mechanical destruction. The results of pyrometric measurement of the melting points in vacuum described in Table 2 (the numbering in Tables 2, 3 is the same).

Table 2

Compositions of the initial mixtures, parameters of sintering (temperature, *T*, pressure, *p*, holding time, *τ*), the phase composition, density, porosity of the consolidated materials and the unit cell parameters (*a*, *b*, *c*) of the phases present in ZrB<sub>2</sub>- and HfB<sub>2</sub>-based materials

No.	Initial composition	<i>P</i> , <i>T</i> , <i>t</i>	Phase composition, wt. %, density, g/cm <sup>3</sup> , porosity, <i>P</i> , %	Unit cell parameters, nm, <i>a</i> , <i>b</i> , <i>c</i>
1	ZrB <sub>2</sub>	<i>P</i> =4.1 GPa <i>T</i> =1800 °C <i>τ</i> =0.13 h	ZrB <sub>2</sub> =100 %, <i>γ</i> =6.2 g/cm <sup>3</sup> , <i>P</i> =0 %	<i>a</i> – 0.3168 <i>c</i> – 0.3528
2	ZrB <sub>2</sub> -20 % SiC	<i>P</i> =4.1 GPa <i>T</i> =1800 °C <i>τ</i> =0.13 h	ZrB <sub>2</sub> =79.53 %, <i>β</i> -SiC=20.47 %, <i>γ</i> =5.04 g/cm <sup>3</sup> , <i>P</i> =1.96 %	<i>a</i> – 0.3169 <i>c</i> – 0.3508 <i>a</i> – 0.4359
3	ZrB <sub>2</sub> -20 % SiC-4 % Si <sub>3</sub> N <sub>4</sub>	<i>P</i> =4.1 GPa <i>T</i> =1800 °C <i>τ</i> =0.13 h	ZrB <sub>2</sub> =77.58 %, <i>β</i> -SiC=19.92 %, <i>β</i> -Si <sub>3</sub> N <sub>4</sub> =2.50 %, <i>γ</i> =4.98 g/cm <sup>3</sup> , <i>P</i> =1.77 %	<i>a</i> – 0.3168 <i>c</i> – 0.3529 <i>a</i> – 0.4357 <i>a</i> – 0.7609 <i>c</i> – 0.2906
4	HfB <sub>2</sub>	<i>P</i> =4.1 GPa <i>T</i> =1800 °C <i>τ</i> =0.13 h	HfB <sub>2</sub> =100 %, <i>γ</i> =10.42 g/cm <sup>3</sup> , <i>P</i> =1 %	<i>a</i> – 0.3141 <i>c</i> – 0.3473
5	HfB <sub>2</sub> -30 % SiC	<i>P</i> =4.1 GPa <i>T</i> =1800 °C <i>τ</i> =0.13 h	HfB <sub>2</sub> =72.40 %, <i>β</i> -SiC=27.60 %, <i>γ</i> =6.21 g/cm <sup>3</sup> , <i>P</i> =3.86 %	<i>a</i> – 0.3143 <i>c</i> – 0.3475 <i>a</i> – 0.4358

Table 4 shows the results of estimation of Young's modulus, Poisson's ratio of the samples sintered under high pressure.

The materials were practically non-porous, but the materials with addition of silicon carbide (samples 2, 3, 4 see Table 2) showed somewhat higher porosity. But their porosity was calculated using the results of X-ray phase analysis (obtained by Reitveld refinement) which are not so exact. Additives (ZrB<sub>2</sub>-20 % SiC (sample 2) and HfB<sub>2</sub>-30 % SiC (sample 5)) led to a decrease in specific gravity and increase in hardness (for 17 % and 46 % as compare with that of ZrB<sub>2</sub> (sample 1) and HfB<sub>2</sub> (sample 4), respectively, Table 3) and fracture toughness (for 40 % and 21 % as compare with that of ZrB<sub>2</sub> and HfB<sub>2</sub>, respectively, Table 3), but significantly reduced the onset temperature

of melting in vacuum down to 2150–2160 °C (Table 3). Materials sintered from ZrB<sub>2</sub> and HfB<sub>2</sub> could not be melted when heated to 2970 °C. At this temperature, the samples were cracked and further heating was not possible. If to prepare samples with thicker walls, the power of the available laser occurred to be not enough to heat them at all.

(with density 6.21 g/cm<sup>3</sup>) had  $H_V(9.8\text{ N})=38.1\pm 1.4\text{ GPa}$ ,  $H_V(49\text{ N})=27.7\pm 2.8\text{ GPa}$ , and  $K_{1C}(9.8\text{ N})=8.1\text{ MH}\cdot\text{m}^{0.5}$ ,  $K_{1C}(49\text{ N})=6.8\text{ MH}\cdot\text{m}^{0.5}$ . The sintered from ZrB<sub>2</sub>-20 % SiC material had density of 5.04 g/cm<sup>3</sup>,  $H_V(9.8\text{ N})=24.2\pm 1.9\text{ GPa}$ ,  $H_V(49\text{ N})=16.7\pm 2.8\text{ GPa}$ ,  $K_{1C}(9.8\text{ N})=7.1\text{ MH}\cdot\text{m}^{0.5}$ . The additions lead to decrease of Young modulus and increase of Poisson ratio (Table 4).

**Table 3**  
Vickers hardness and fracture toughness of the ZrB<sub>2</sub> and HfB<sub>2</sub>-based materials before and after heating. Numbering is the same as in the Table 2

Sample No.	Initial composition	Heating temperature	Vickers hardness, GPa, under the load			Fracture toughness, $K_{1C}$ , MPa·m <sup>0.5</sup> , under the load		
			9.8 N	49 N	98 N	9.8 N	49 N	98 N
1	ZrB <sub>2</sub>	–	17.7	15.4	15.3	4.3	4.2	4.0
1*	ZrB <sub>2</sub>	Crack under 2970 °C	14.42	7.85	8.35	3.1	3.46	3.83
2	ZrB <sub>2</sub> -20 % SiC	–	24.2	16.7	17.6	–	7.1	6.2
2*	ZrB <sub>2</sub> -20 % SiC	2160 °C	12.95	11.29	10.61	2.77	4.84	3.95
3	ZrB <sub>2</sub> -20 % SiC-4 % Si <sub>3</sub> N <sub>4</sub>	–	20.5	18.3	15.8	–	–	9.2
3*	ZrB <sub>2</sub> -20 % SiC-4 % Si <sub>3</sub> N <sub>4</sub>	2160 °C	16.87	11.76	11.32	4.65	5.53	5.07
4	HfB <sub>2</sub>	–	21.3	19.3	19.2	–	7.2	5.7
4*	HfB <sub>2</sub>	Crack under 2970 °C	11.95	5.05	6.57	1.68	2.14	2.57
5	HfB <sub>2</sub> -30 % SiC	–	38.0	27.7	26.3	8.2	6.8	6.4
5*	HfB <sub>2</sub> -30 % SiC	2150 °C	22.59	21.52	21.28	–	7.56	7.46

Note: \* – sample after heating and pyrometric measurement of melting point

**Table 4**  
Mechanical characteristics of ceramics. Numbering is the same as in the Table 2

Sample No.	Initial composition	Speed of sound, $s$ , m/s	Young's modulus, $E$ , GPa	Log. decrement of oscillations, %	Poisson ratio, $\mu$
1	ZrB <sub>2</sub>	8291	418	0.971	0.093
2	ZrB <sub>2</sub> -20 % SiC	8599	358	1.576	0.146
3	ZrB <sub>2</sub> -20 % SiC-4 % Si <sub>3</sub> N <sub>4</sub>	8566	358	2.258	0.146
4	HfB <sub>2</sub>	8941	847	0.973	0.093

Composite material prepared from ZrB<sub>2</sub>-20 % SiC-4 % Si<sub>3</sub>N<sub>4</sub> (sample 3) demonstrated somewhat lower hardness than that prepared from ZrB<sub>2</sub>-20 % SiC (sample 2), but higher fracture toughness (Table 3).

After heating to a melting point of 2150–2160 °C (in the case of materials with additives) and to temperatures of 2970 °C (in the case of materials sintered with ZrB<sub>2</sub> or HfB<sub>2</sub>), the hardness and crack resistance decreased (Table 3). Thus, the hardness of the material prepared from ZrB<sub>2</sub> decreased by 19 % and its crack resistance – by 18 %, and of that prepared from ZrB<sub>2</sub>-20 % SiC – by 46 % and 32 %, respectively. The hardness of the material prepared from HfB<sub>2</sub> decreased by 46 %, its crack resistance – by 55 %, and of that prepared from HfB<sub>2</sub>-30 % SiC, after heating decreased by 40 %, but its fracture toughness increased by 15 %. The sintered HfB<sub>2</sub> (with a density of 10.4 g/cm<sup>3</sup>) before heating showed hardness of  $H_V(9.8\text{ N})=21.27\pm 0.84\text{ GPa}$ ,  $H_V(49\text{ N})=19.29\pm 1.34\text{ GPa}$  and  $H_V(98\text{ N})=19.17\pm 0.5\text{ GPa}$ , and fracture toughness  $K_{1C}(9.8\text{ N})=6.47\text{ MH}\cdot\text{m}^{0.5}$ , and ZrB<sub>2</sub> with density of 6.2 g/cm<sup>3</sup> was characterized by  $H_V(9.8\text{ N})=17.66\pm 0.60\text{ GPa}$ ,  $H_V(49\text{ N})=15.25\pm 1.22\text{ GPa}$  and  $H_V(98\text{ N})=15.32\pm 0.36\text{ GPa}$ ,  $K_{1C}(9.8\text{ N})=4.3\text{ MH}\cdot\text{m}^{0.5}$ . The material sintered from HfB<sub>2</sub>-30 % SiC


The X-ray study (Table 2) showed that after sintering materials with additions have similar phase composition as the initial mixture, but SEM EDX study showed that their structures are somewhat more complicated. The structure of the material prepared from ZrB<sub>2</sub>-20 % SiC is shown in Table 5, Fig. 1. Thus, sample 2 sintered at high pressures consisted of three main phases, whose stoichiometry is close to the  $Z_{0.9}B_2C_{0.12-0.19}$ ,  $Si_{0.92-0.94}C$ ,  $Si_{0.94-0.99}CO_{0.05-0.06}$ .

Comparing the results of hardness tests, with the literature data, one can see a pronounced effect of the sintering pressure. The Vickers hardness under indentation load 9.8 N of sample 1 from ZrB<sub>2</sub> is 17.7 GPa, of sample 3 from ZrB<sub>2</sub>-20 % SiC is 24.2 GPa, of sample 4 from HfB<sub>2</sub> is 21.3 GPa, while according [12, 13] the materials prepared from the same initial powders and mixtures but under lower pressures (50 MPa) and higher temperatures (1950–2100 °C) demonstrated somewhat lower hardnesses under the same load: 16.5, 21.1 and 19.8 GPa, respectively.

**Table 5**  
The results of a microprobe analysis in % of the material prepared from ZrB<sub>2</sub>-20 % SiC

Spec-trum	B	C	O	Si	Zr	Total	Approximate composition
S1	65.43	5.93	–	–	28.64	100	Z <sub>0.9</sub> B <sub>2</sub> C <sub>0.18</sub>
S2	65.64	3.97	–	–	30.39	100	Z <sub>0.9</sub> B <sub>2</sub> C <sub>0.12</sub>
S3	65.18	4.86	–	–	29.96	100	Z <sub>0.91</sub> B <sub>2</sub> C <sub>0.14</sub>
S4	65.08	6.16	–	–	28.75	100	Z <sub>0.88</sub> B <sub>2</sub> C <sub>0.19</sub>
S5	65.15	5.52	–	–	29.32	100	Z <sub>0.9</sub> B <sub>2</sub> C <sub>0.17</sub>
S6	–	48.09	–	51.91	–	100	Si <sub>0.93</sub> C
S7	–	48.8	2.89	48.31	–	100	Si <sub>0.99</sub> CO <sub>0.06</sub>
S8	–	49.14	–	50.86	–	100	Si <sub>0.97</sub> C
S9	–	48.41	–	51.59	–	100	Si <sub>0.94</sub> C
S10	–	50.41	2.28	47.31	–	100	Si <sub>0.94</sub> CO <sub>0.05</sub>
S11	–	47.94	–	52.06	–	100	Si <sub>0.92</sub> C
S12	65.34	4	–	–	30.66	100	Z <sub>0.94</sub> B <sub>2</sub> C <sub>0.12</sub>



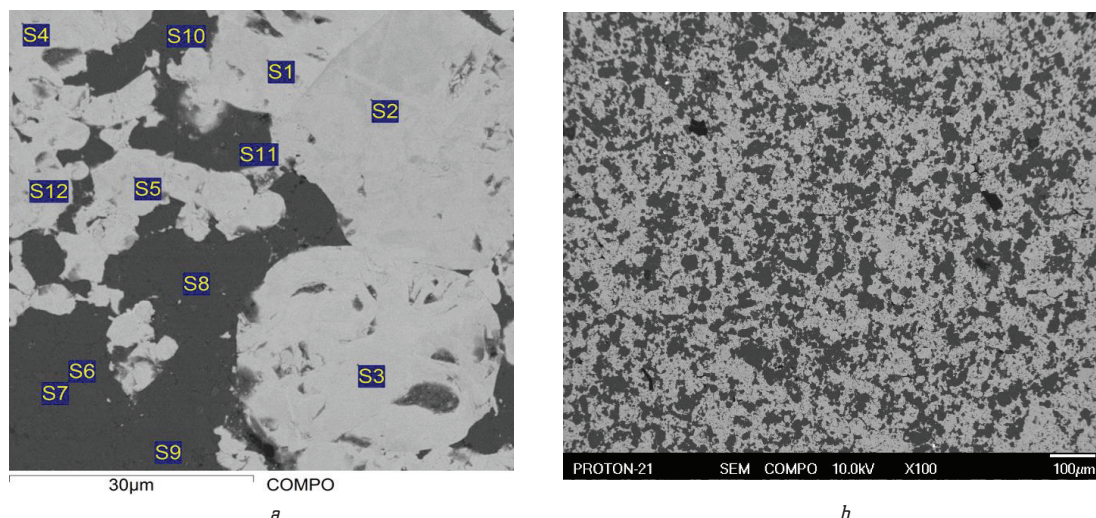

**Fig. 1.** Structure of sample 2 (see Table 2) obtained sintering from  $ZrB_2$ -20 % SiC (see Table 2) using the SEM in a regime:  
a – COMPO 30  $\mu$ m; b – COMPO 100  $\mu$ m

The temperature of the onset of melting of No. 1\* ( $ZrB_2$ ) and No. 5\* ( $HfB_2$ ) could not be measured. The samples were heated to 2970 °C, after which they cracked in half.  $ZrB_2$  is usually melts at 3250 °C according to the phase diagrams [14, 15]. However, other researchers report different melting points, including 3040 °C [16] and 3517 °C [17]. The reason for these discrepancies lies not only in the difficulty of accurately measuring melting points at high temperatures, but also in the fact that these compounds melt incongruently, i. e. they can decompose or dissociate before melting.

The temperature of the beginning of melting of specimens samples 2\* ( $ZrB_2$ -20SiC), 3\* ( $ZrB_2$ -20SiC-4Si<sub>3</sub>N<sub>4</sub>) and 5\* ( $HfB_2$ -30SiC) were estimated as 2160 °C. The character of melting was violent. As it was mentioned above the additions of SiC to  $ZrB_2$  and  $HfB_2$  lowers the melting points of the materials.

In the works of other researchers, it is reported that  $ZrB_2$  had a Young modulus of 222.1 GPa [18] and that hot-pressed polycrystalline  $ZrB_2$  bars showed Young modulus of 503.3 GPa [19]. The material hot pressed under uniaxial pressure of 32 MPa from  $ZrB_2$ -20SiC powder mixtures at a temperature of 1900 °C demonstrated Young's modulus showed 479 GPa [20]. The composite sintered from  $ZrB_2$ -20SiC-4Si<sub>3</sub>N<sub>4</sub> powders under uniaxial pressure of 30 MPa at 2000 °C in an argon atmosphere showed Young modulus 467 GPa [21]. In our case,  $ZrB_2$  sintered at 4.1 GPa and 1800 °C demonstrated Young modulus 418 GPa (Table 4). The SiC addition to the initial mixture significantly reduces the elasticity of the materials (Table 4).

#### 4. Conclusions

The investigation of structure and materials mechanical properties sintered at high (4.1 GPa) pressure and 1800 °C from  $HfB_2$ ,  $ZrB_2$  without and with additives of SiC and Si<sub>3</sub>N<sub>4</sub> allowed conclude the following.

The additives led to a decrease in specific gravity and increase in hardness and fracture toughness, decrease Young modulus, increase Poisson ratio and significantly reduce the onset of melting temperature in vacuum (down to 2150–2160 °C).

#### Acknowledgements

The investigations were performed in the frames of the project NATO SPS G5773 «Advanced Material Engineering to Address Emerging Security Challenges» for 2020–2023, the project 03-03-20 of Ukrainian-Belorusian cooperation for 2019–2020, and the National Acad. Sci. of Ukraine project under «Support for development of priority national research» program under Contract No. ISM-29/20 (II-5-19), the projects III-3-20 (0779) and III-5-19 (0778) supported by the National Academy of Sciences of Ukraine.

#### References

1. Upadhyaya, K., Yang, J. M., Hoffmann, W. P. (1997). Materials for ultra high temperature structural applications. *American Ceramic Society Bulletin*, 76, 51–56.
2. Sichkar, S. M., Antonov, V. N., Antropov, V. P. (2013). Comparative study of the electronic structure, phonon spectra, and electron-phonon interaction of  $ZrB_2$  and  $TiB_2$ . *Physical Review B*, 87 (6). doi: <http://doi.org/10.1103/physrevb.87.064305>
3. Zhang, G.-J., Guo, W.-M., Ni, D.-W., Kan, Y.-M. (2009). Ultrahigh temperature ceramics (UHTCs) based on  $ZrB_2$  and  $HfB_2$  systems: Powder synthesis, densification and mechanical properties. *Journal of Physics: Conference Series*, 176, 012041. doi: <http://doi.org/10.1088/1742-6596/176/1/012041>
4. Guo, S.-Q. (2009). Densification of  $ZrB_2$ -based composites and their mechanical and physical properties: A review. *Journal of the European Ceramic Society*, 29 (6), 995–1011. doi: <http://doi.org/10.1016/j.jeurceramsoc.2008.11.008>
5. Squire, T. H., Marschall, J. (2010). Material property requirements for analysis and design of UHTC components in hypersonic applications. *Journal of the European Ceramic Society*, 30 (11), 2239–2251. doi: <http://doi.org/10.1016/j.jeurceramsoc.2010.01.026>
6. McCusker, L. B., Von Dreele, R. B., Cox, D. E., Louër, D., Scardi, P. (1999). Rietveld refinement guidelines. *Journal of Applied Crystallography*, 32 (1), 36–50. doi: <http://doi.org/10.1107/s0021889898009856>
7. Glagovskii, B. A., Roitshtein, G. Sh., Iashin, V. A. (1980). *Kontrolno-izmeritelnye pribori i osnovi avtomatizatsii proizvodstva abrazivnykh instrumentov*. Leningrad: Mashinostroenie, 278.
8. Baranov, V. M. (1972). Opredelenie konstant uprugosti obratsovo materialov, imeiuschikh formu diska. *Zavodskaja laboratorija*, 9, 1120–1124.
9. Pirani, M., Alterthum, H. (1923). On a method for determining the melting point of refractory metals. *Z. Elektrochem.*, 29 (1–2), 5–8.

10. Bondar, A. A., Maslyuk, V. A., Velikanova, T. Y., Grytsiv, A. V. (1997). Phase equilibria in the Cr-Ni-C system and their use for developing physicochemical principles for design of hard alloys based on chromium carbide. *Powder Metallurgy and Metal Ceramics*, 36 (5-6), 242–252. doi: <http://doi.org/10.1007/bf02676213>
11. Velikanova, T. Y., Bondar, A. A., Grytsiv, A. V. (1999). The chromium-nickel-carbon (Cr-Ni-C) phase diagram. *Journal of Phase Equilibria*, 20 (2), 125–147. doi: <http://doi.org/10.1007/s11669-999-0011-3>
12. Zapata-Solvas, E., Jayaseelan, D. D., Lin, H. T., Brown, P., Lee, W. E. (2013). Mechanical properties of ZrB<sub>2</sub>- and HfB<sub>2</sub>-based ultra-high temperature ceramics fabricated by spark plasma sintering. *Journal of the European Ceramic Society*, 33 (7), 1373–1386. doi: <http://doi.org/10.1016/j.jeurceramsoc.2012.12.009>
13. Prikhna, T., Lokatkina, A., Moshchil, V., Barvitskiy, P., Borimsky, O., Ponomaryov, S. et. al. (2020). Investigation of mechanical characteristics of materials based on refractory borides. *Technology Audit and Production Reserves*, 6 (1 (56)), 40–44. doi: <http://doi.org/10.15587/2706-5448.2020.220320>
14. Rudy, E. (1969). Ternary phase equilibria in transition metal-boron-carbon systems: part V, compendium of phase diagram data. *Technical Report AFML-TR-65-2. Wright Patterson Air Force Base (OH): Air Force Materials Laboratory.*
15. Portnoi, K. I., Romashov, V. M., Salibekov, S. E. (1971). Constitution diagram of the system tantalum-boron. *Soviet Powder Metallurgy and Metal Ceramics*, 10 (11), 925–927. doi: <http://doi.org/10.1007/bf00794010>
16. Glasser, F. W., Post, B. (1953). Phase diagram zirconium-boron. *Trans Metallurgical Soc AIME*, 197, 1117–1118.
17. Rogl, P., Potter, P. E. (1988). A critical review and thermodynamic calculation of the binary system: Zirconium-boron. *Calphad*, 12 (2), 191–204. doi: [http://doi.org/10.1016/0364-5916\(88\)90021-1](http://doi.org/10.1016/0364-5916(88)90021-1)
18. Neschpor, V. S., Samsonov, G. V. (1957). The brittleness of metallike compound. *Fiz.:Metal. i Metalloved.*, 4, 181.
19. Wiley, D. E., Manning, W. R., Hunter, O. (1969). Elastic properties of polycrystalline TiB<sub>2</sub>, ZrB<sub>2</sub> and HfB<sub>2</sub> from room temperature to 1300 °K. *Journal of the Less Common Metals*, 18 (2), 149–157. doi: [http://doi.org/10.1016/0022-5088\(69\)90134-9](http://doi.org/10.1016/0022-5088(69)90134-9)
20. Zhu, S., Fahrenholtz, W. G., Hilmas, G. E. (2007). Influence of silicon carbide particle size on the microstructure and mechanical properties of zirconium diboride-silicon carbide ceramics. *Journal of the European Ceramic Society*, 27 (4), 2077–2083. doi: <http://doi.org/10.1016/j.jeurceramsoc.2006.07.003>
21. Mallik, M., Ray, K., Mitra, R. (2017). Effect of Si<sub>3</sub>N<sub>4</sub> Addition on Oxidation Resistance of ZrB<sub>2</sub>-SiC Composites. *Coatings*, 7 (7), 92. doi: <http://doi.org/10.3390/coatings7070092>

**Anastasiia Lokatkina**, Postgraduate Student, Department of High-Pressure Technologies, Functional Ceramic Composites and Disperse Superhard Materials, V. Bakul Institute for Superhard Materials of National Academy of Sciences of Ukraine, Kyiv, Ukraine, e-mail: [aslokatkina@gmail.com](mailto:aslokatkina@gmail.com), ORCID: <https://orcid.org/0000-0001-6778-117X>

**Tetiana Prikhna**, Doctor of Technical Science, Professor, Corresponding Member of National Academy of Sciences of Ukraine, Head of Department of High-Pressure Technologies, Functional Ceramic Composites and Disperse Superhard Materials, V. Bakul Institute for Superhard Materials of National Academy of Sciences of Ukraine, Kyiv, Ukraine, e-mail: [prikhna@ukr.net](mailto:prikhna@ukr.net), ORCID: <https://orcid.org/0000-0002-1621-0681>

**Viktor Moshchil**, Senior Researcher, Department of High-Pressure Technologies, Functional Ceramic Composites and Disperse Superhard Materials, V. Bakul Institute for Superhard Materials of National Academy of Sciences of Ukraine, Kyiv, Ukraine, e-mail: [vik\\_ism@ukr.net](mailto:vik_ism@ukr.net), ORCID: <https://orcid.org/0000-0003-2147-067X>

**Pavlo Barvitskiy**, Junior Research, Department of High-Pressure Technologies, Functional Ceramic Composites and Disperse Superhard Materials, V. Bakul Institute for Superhard Materials of National Academy of Sciences of Ukraine, Kyiv, Ukraine, e-mail: [barvitskp@gmail.com](mailto:barvitskp@gmail.com), ORCID: <https://orcid.org/0000-0002-7594-8619>

**Oleksandr Borimsky**, Leading Researcher, Department of High-Pressure Technologies, Functional Ceramic Composites and Disperse Superhard Materials, V. Bakul Institute for Superhard Materials of National Academy of Sciences of Ukraine, Kyiv, Ukraine, e-mail: [lab7@ism.kiev.ua](mailto:lab7@ism.kiev.ua), ORCID: <https://orcid.org/0000-0002-3104-4976>

**Leonid Devin**, Leading Researcher, Department of Physical and Mechanical Research and Nanotesting of Materials, V. Bakul Institute for Superhard Materials of National Academy of Sciences of Ukraine, Kyiv, Ukraine, e-mail: [ldevin350@gmail.com](mailto:ldevin350@gmail.com), ORCID: <https://orcid.org/0000-0002-1452-9904>

**Semyon Ponomaryov**, Junior Researcher, Department of Optics and Spectroscopy for Electrical and Electrical Materials, V. E. Lashkaryov Institute of Semiconductor Physics of the National Academy of Sciences of Ukraine, Kyiv, Ukraine, e-mail: [s.s.ponomaryov@gmail.com](mailto:s.s.ponomaryov@gmail.com), ORCID: <https://orcid.org/0000-0003-4548-4275>

**Richard Haber**, Professor, Co-Director, Ceramic, Composite and Optical Materials Center, Department of Materials Science and Engineering, Rutgers, The State University of New Jersey, New Brunswick, USA, e-mail: [rhaber1@rci.rutgers.edu](mailto:rhaber1@rci.rutgers.edu), ORCID: <https://orcid.org/0000-0002-0399-2530>

**Tatiana Talako**, Leading Researcher, State Scientific Institution «Powder Metallurgy Institute», Minsk, Belarus, e-mail: [talako@tut.by](mailto:talako@tut.by), ORCID: <https://orcid.org/0000-0002-3156-105X>

**Anatoly Bondar**, Senior Researcher, Department No. 6 of Physical Chemistry of Inorganic Materials, Institute for Problems of Materials Sciences of National Academy of Sciences of Ukraine, Kyiv, Ukraine, e-mail: [aa\\_bondar@ukr.net](mailto:aa_bondar@ukr.net), ORCID: <https://orcid.org/0000-0001-7855-4909>